

UC Irvine

UC Irvine Previously Published Works

Title

Phonon Raman scattering in superconducting $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$

Permalink

<https://escholarship.org/uc/item/0b05d9tq>

Journal

Physical Review B, 35(16)

ISSN

2469-9950

Authors

Blumenroeder, S
Zirngiebl, E
Thompson, JD
[et al.](#)

Publication Date

1987-06-01

DOI

10.1103/physrevb.35.8840

Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>

Peer reviewed

Phonon Raman scattering in superconducting $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ S. Blumenroeder, E. Zirngiebl, J. D. Thompson, P. Killough, J. L. Smith, and Z. Fisk
Los Alamos National Laboratory, Los Alamos, New Mexico 87545

(Received 23 March 1987)

We have performed Raman scattering experiments on the high- T_c superconductor $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ ($T_c \approx 37$ K). We observe three of the four Raman-active optical-phonon modes and, on the basis of a comparison to the Raman spectra of K_2MnF_4 , are able to tentatively assign the mode symmetries. No anomalous temperature dependence is observed for all three modes, indicative of the lack of strong electron-phonon coupling in these modes.

Recently superconductivity in the system $(\text{La}, X)_2\text{CuO}_{4-y}$ ($X = \text{Ba}, \text{Sr}$) has been found¹⁻⁴ with transition temperatures T_c up to ~ 40 K, which is almost 100% higher than the previously highest T_c of about 23 K in Nb_3Ge .⁵ In the conventional BCS theory of superconductivity, a high T_c results from strong electron-phonon coupling. Strong electron-phonon coupling is anticipated for $(\text{La}, \text{Sr})_2\text{CuO}_4$ due to the nearly ideal nesting conditions of the Fermi surface that arise from the planar structure of this compound.⁶ Indeed, a Peierls transition in undoped $\text{La}_2\text{CuO}_{4-y}$ from tetragonal to orthorhombic crystal structure is found⁷ at 260°C . However, there also has been the suggestion⁸ that Cooper pairing in this new class of high- T_c materials does not arise from phonon coupling but is primarily due to electronic coupling produced by resonating Cu—O valence bonds. This is appealing because, as McMillan⁹ pointed out, soft phonons, which are responsible in part for enhanced electron-phonon coupling, also lead to lattice instabilities and can place an upper limit on T_c . Subsequent work by Allen and co-workers^{10,11} showed that McMillan's constraints were unnecessarily severe, but that there may still be a limiting value for T_c . In any case, microscopic information on the lattice dynamics of $(\text{La}, \text{Sr})_2\text{CuO}_{4-y}$ is highly desirable to arrive at a microscopic understanding of superconductivity in this new class of high- T_c superconductors.

We have performed Raman scattering experiments on $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ in an attempt to reveal the basic mechanism for Cooper pairing in this compound. Our sample was made by grinding the oxides and firing the pressed mixture three times at 1100°C in an oxygen atmosphere. The resulting powder was pressed into a pellet. The superconducting transition temperature was deter-


mined to be 37 K from dc magnetic-susceptibility measurements¹² which also showed diamagnetism of 55% of $1/4\pi$ at 2 K, when the sample was cooled in zero applied field below T_c . $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ crystallizes in the tetragonal space group D_{4h}^{17} ($I4/mmm$) having two formula units per unit cell. The different $q=0$ phonon modes of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ are listed in Table I, with the four Raman-active (RA) modes displayed¹³ in Fig. 1. One A_{1g} and one E_g mode are due to oxygen vibrations and the other A_{1g} and E_g modes result from movements of the lanthanum ion.

In Fig. 2 we show Raman spectra of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ as a function of temperature. Because our sample was polycrystalline, we could not perform a symmetry analysis of the observed peaks. However, from comparison with the symmetry analysis of the Raman spectrum of isostructural K_2MnF_4 (Ref. 14) or K_2CuF_4 ,¹⁵ we can tentatively assign the peaks in Fig. 2 to the following symmetries: The lanthanum A_{1g} mode is at 100 cm^{-1} scaled down from the value of the potassium A_{1g} mode in K_2MnF_4 (180 cm^{-1}) by the square root of

TABLE I. Factor-group analysis of the $q=0$ lattice vibrations of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_4$ crystallizing in the K_2NiF_4 structure (D_{4h}^{17} or $I4/mmm$).

Type	Symmetry
Raman active	$2 \times A_{1g}, 2 \times E_g$
Infrared active	$3 \times A_{2u}, 4 \times E_u, 1 \times B_{2u}$
Translational (acoustic modes)	$1 \times A_{2u}, 1 \times E_u$
Others	...

(a) OXYGEN VIBRATIONS

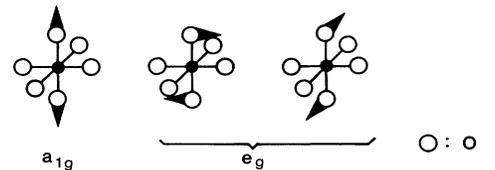

(b) LANTHANUM VIBRATIONS

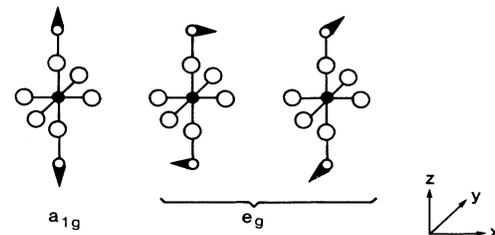


FIG. 1. Raman-active modes of $(\text{La}_{1.85}\text{Sr}_{0.15})\text{CuO}_{4-y}$ with D_{4h}^{17} . Filled circles denote Cu atoms, large open circles O-atoms, and small open circles La atoms (Sr atoms), respectively.

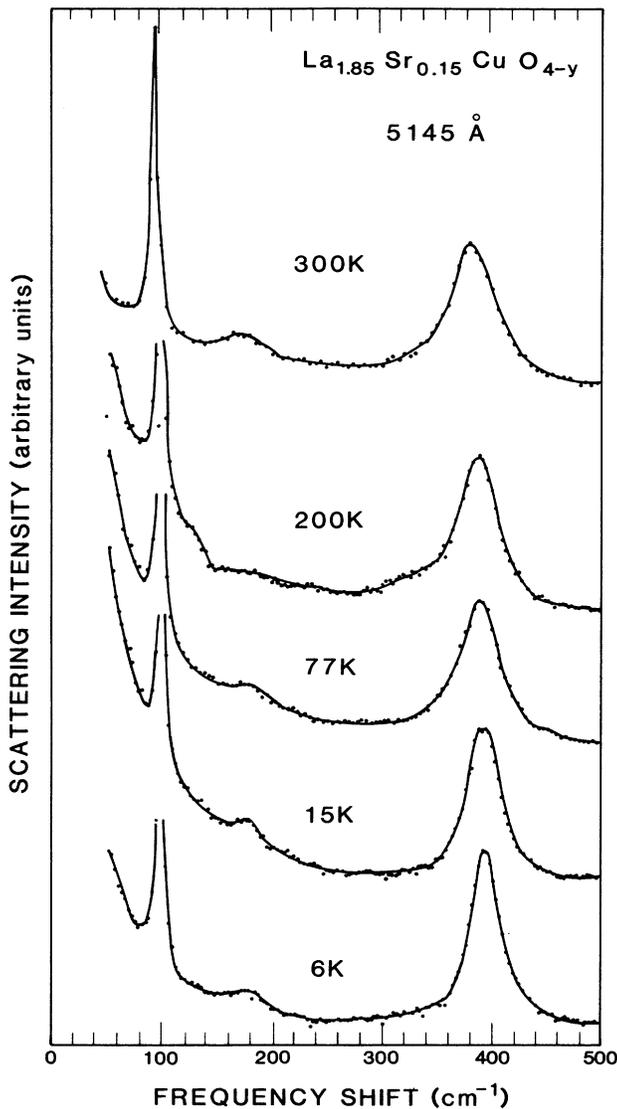


FIG. 2. Raman spectra of $(\text{La}_{1.85}\text{Sr}_{0.15})\text{CuO}_{4-y}$ for selected temperatures between 300 and 6 K. The oxygen A_{1g} mode is near 400 cm^{-1} , the oxygen E_g mode near 180 cm^{-1} , and the lanthanum (strontium) A_{1g} mode near 100 cm^{-1} .

the mass ratio of potassium and lanthanum. The lanthanum E_g mode consequently is expected at 50 cm^{-1} and is probably too weak in intensity to be observed, as we tried without success to find any mode in that energy region. The oxygen A_{1g} mode is at 380 cm^{-1} similar to the fluorine A_{1g} mode in K_2MnF_4 and the oxygen E_g mode is near 180 cm^{-1} also in good agreement from what is expected from the reference compounds. The oxygen A_{1g} mode is, however, broader and weaker compared to the fluorine A_{1g} mode in K_2MnF_4 .

Variation of the temperature has little effect on the Raman spectra of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ as can be seen from Fig. 2. In Figs. 3 and 4 the linewidths and peak positions, respectively, are plotted as a function of temperature for the lanthanum A_{1g} mode and the oxygen A_{1g} mode. The

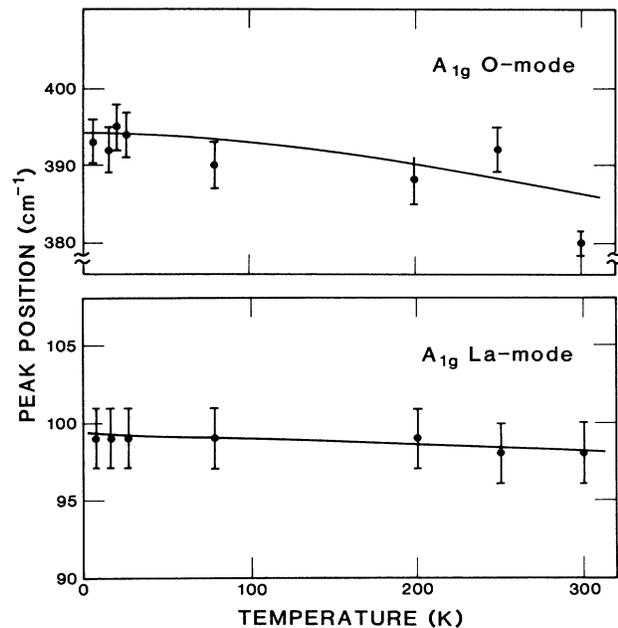


FIG. 3. Peak position of the oxygen A_{1g} mode and the lanthanum A_{1g} mode as a function of temperature.

signal of the oxygen E_g mode was too weak to yield reliable detailed information. The lanthanum A_{1g} mode does not have a significant temperature dependence in either its position or its linewidth. It is, however, surprising that we do not observe a splitting of this peak due to the presence of Sr, since its mass is quite different from that of La. In

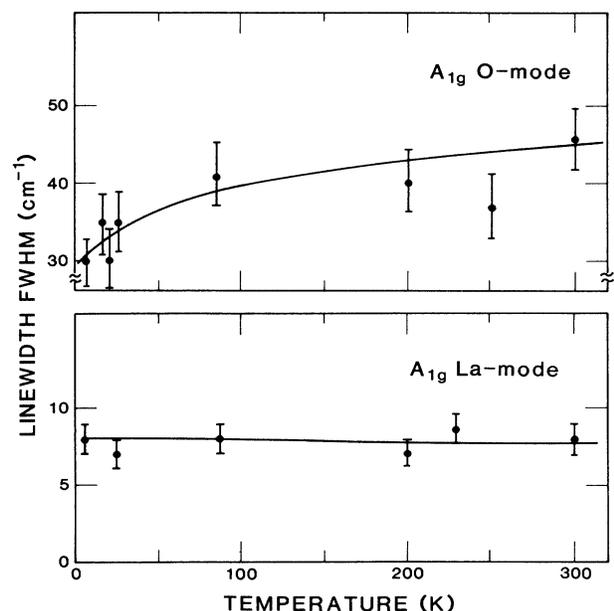


FIG. 4. Linewidth (full width at half maximum) of the oxygen A_{1g} mode and the lanthanum A_{1g} mode as a function of temperature.

any case, this is indicative of a very homogeneous mixing of the Sr into the lattice. For the oxygen A_{1g} mode one observes an unusually large linewidth (46 cm^{-1} at 300 K). This is probably related to oxygen deficiencies, which are anticipated for $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ from the behavior of all perovskites.^{1,16} Deficiencies break the translational invariance of the system, thereby destroying q conservation and allowing Raman scattering from $q \neq 0$ oxygen modes. Because these modes are not dispersionless, this results in line broadening. This can also cause a shift in peak position, and a spatially inhomogeneous distribution of oxygen deficiencies could, therefore, explain the scatter in the peak position of the oxygen A_{1g} mode, as can be seen from Fig. 3. This is not observed for the lanthanum A_{1g} mode. As a general trend of the data we observe, similar to the behavior of the lanthanum A_{1g} mode, a broadening of the oxygen A_{1g} mode and a nearly temperature-independent peak position.

To summarize our experimental results, the observed Raman-active phonons of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ do not reflect strong electron-phonon coupling effects, which should result in a softening and line broadening of these modes upon cooling the sample below T_c . The large linewidth of the oxygen A_{1g} mode is quite unusual and seems to be related to oxygen deficiencies in our sample.

Our Raman scattering results can be put in the following way into the context of what is known or imagined about $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4-y}$. Most simply one could say, if

the Cooper pairing of the electrons is primarily electronic in nature, one should of course not observe any phonon anomalies. On the other hand, phonons modulating the Cu—O bond lengths in the x - y plane, which are only infrared (IR) active, should exhibit the strongest electron-phonon coupling because they provide the nesting of the Fermi surface in pure $\text{La}_2\text{CuO}_{4-y}$. Consequently, probably the most pronounced electron-phonon coupling cannot be probed by Raman scattering, and our results do not completely rule out strong electron-phonon coupling in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$. Absence or presence of strong electron-phonon coupling in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$ has to be proven conclusively by IR spectroscopy or neutron scattering. However, it is surprising that a strong electron-phonon coupling in the Cu-O planes, necessary to explain a T_c of 37 K in conventional BCS terms, should have absolutely no effect on the lattice dynamics of those layers not containing Cu.

In conclusion, we have observed three of the four Raman-active modes of $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$, none of them exhibiting features indicative of strong electron-phonon coupling. Because Raman scattering is insensitive to phonons modulating the Cu—O bonds, our results do not permit a definitive statement concerning the pairing mechanism in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_{4-y}$.

This work was performed under the auspices of the Department of Energy.

¹J. G. Bednorz and K. A. Müller, *Z. Phys. B* **64**, 189 (1986).

²C. W. Chu, P. H. Hor, R. L. Meng, L. Gao, Z. J. Huang, and Y. Q. Wang, *Phys. Rev. Lett.* **58**, 405 (1987).

³S. Uchida, H. Takagi, K. Kitazawa, and S. Tanaka, *Jpn. J. Appl. Phys.* **26**, L1 (1987).

⁴R. J. Cava, R. B. Van Dover, B. Batlogg, and E. A. Rietman, *Phys. Rev. Lett.* **58**, 408 (1987).

⁵J. R. Gavaler, *Appl. Phys. Lett.* **23**, 480 (1973).

⁶F. Mueller (private communication).

⁷J. M. Longo and P. M. Raccach, *J. Solid State Chem.* **6**, 526 (1973).

⁸P. W. Anderson (unpublished).

⁹W. L. McMillan, *Phys. Rev.* **167**, 331 (1968).

¹⁰P. B. Allen and R. C. Dynes, *Phys. Rev. B* **12**, 905 (1975).

¹¹P. B. Allen and B. Mitrovic, *Solid State Phys.* **37**, 1 (1982).

¹²S. Blumenroeder, E. Zirngiebl, J. D. Thompson, J. L. Smith, and Z. Fisk (unpublished).

¹³Y. Natsume and I. Yamada, *J. Phys. Soc. Jpn.* **54**, 4410 (1985).

¹⁴W. Lehmann and R. Weber, *Phys. Lett.* **45A**, 33 (1973).

¹⁵M. Kaneko, G. Kuwabara, and A. Misu, *Solid State Commun.* **18**, 1085 (1976).

¹⁶J. M. Tarascon, L. H. Greene, W. R. McKinnon, G. W. Hull, and T. H. Geballe (unpublished); K. Kishio, K. Kitazawa, N. Sugii, S. Kanbe, K. Fueki, H. Takagi, and S. Tanaka, *Chem. Lett.* (to be published).