

# UC Davis

## UC Davis Previously Published Works

### Title

Metal–Organic Framework Nodes as Nearly Ideal Supports for Molecular Catalysts: NU-1000- and UiO-66-Supported Iridium Complexes

### Permalink

<https://escholarship.org/uc/item/7w2238h5>

### Journal

Journal of the American Chemical Society, 137(23)

### ISSN

0002-7863

### Authors

Yang, Dong  
Odoh, Samuel O  
Wang, Timothy C  
et al.

### Publication Date

2015-06-17

### DOI

10.1021/jacs.5b02956

Peer reviewed

# Metal-organic framework nodes as nearly ideal supports for molecular catalysts: NU-1000- and UiO-66-supported iridium complexes

Dong Yang,<sup>a</sup> Samuel O. Odoh,<sup>b</sup> Timothy C. Wang,<sup>c</sup> Omar K. Farha,<sup>c,d</sup> Joseph T. Hupp,<sup>c</sup> Christopher J. Cramer,<sup>b</sup> Laura Gagliardi,<sup>b\*</sup> Bruce C. Gates<sup>a\*</sup>

<sup>a</sup> Department of Chemical Engineering & Materials Science, University of California, Davis, California 95616, United States

<sup>b</sup> Department of Chemistry, Chemical Theory Center, and Supercomputing Institute, University of Minnesota, Minneapolis, Minnesota 55455-0431, United States

<sup>c</sup> Department of Chemistry, Northwestern University, 2145 Sheridan Road, Evanston, Illinois 60208, United States

<sup>d</sup> Department of Chemistry, Faculty of Science, King Abdulaziz University, Jeddah 22254, Saudi Arabia

**ABSTRACT:** Metal-organic frameworks with Zr<sub>6</sub> nodes, UiO-66 and NU-1000, were investigated as supports for Ir(CO)<sub>2</sub> and Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub> complexes. A single bonding site for the iridium is identified on the nodes of NU-1000, whereas two sites are identified on UiO-66, although, at low iridium loadings, only one site is occupied. Density functional theory calculations provide structural results that are in good agreement with infrared and X-ray absorption fine structure spectra. The reactivity of node-supported Ir(CO)<sub>2</sub> with C<sub>2</sub>H<sub>4</sub> and the catalytic activity and selectivity of the species initially present as Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub> for ethylene hydrogenation and dimerization were investigated both experimentally and computationally and shown to be strongly influenced by the node.

## 1. INTRODUCTION

Metal-organic frameworks (MOFs) are a class of crystalline and porous materials formed by coordination bonds between metal-containing nodes and organic linkers.<sup>1-3</sup> MOFs that are stable at high temperatures are appealing but still little-investigated as catalyst supports,<sup>4-10</sup> especially for transformations of gas-phase reactants. Several investigators have used the organic linkers of MOFs to anchor metal complexes used as catalysts. For example, Manna *et al.*<sup>11</sup> prepared MOFs with Fe(II) and Co(II) salicylaldimine complexes as linkers, finding them to be highly active for 1-Octene hydrogenation. Fei and Cohen<sup>12</sup> modified the linkers of MOFs to form thiocatechol-functionalized sites for palladium centers that selectively catalyze the oxidative functionalization of aromatic C-H bonds. Gonzalez *et al.*<sup>13</sup> used a MOF with bipyridine sites in the linkers that reacted with Ir(COD)<sub>2</sub>BF<sub>4</sub> (COD is 1,5-cyclooctadiene) to give a catalysts for arene C-H borylation. These catalysts are all comparable to organic polymer-supported catalysts.

Alternatively, MOF nodes that resemble small pieces of metal oxides have been used as catalyst supports that are comparable to metal oxides and zeolites. Larabi and Quadrelli<sup>14</sup> pointed out that the OH groups on such nodes provide sites for bonding of organometallic catalyst precursors. For example, Nguyen *et al.*<sup>15</sup> used the zirconium oxide nodes of UiO-66 as a support for a catalyst synthesized from vanadyl acetylacetonate to convert cyclohexene to benzene by oxidative dehydrogenation; this catalyst was used at temperatures up to 350 °C, pointing to stability advantages of this class of MOF. Mondloch *et al.*<sup>16</sup> also reported the use of such MOF nodes as supports for aluminum and zinc catalysts made by atomic layer deposition of gas-phase catalyst precursors.

Supported metal catalysts that are essentially molecular and structurally well-defined offer numerous advantages for fundamental understanding; such catalysts have been synthesized on the surfaces of zeolites and in prospect can be synthesized similarly on MOF nodes.<sup>17</sup> We now report such catalysts: MOF

node-supported metal complexes that are structurally well defined—both from the viewpoint of the metal species and the support. We selected Zr<sub>6</sub>-based UiO-66 and NU-1000 frameworks because of their exceptional thermal stability and well-defined structures.<sup>16,18</sup> UiO-66 is composed of [Zr<sub>6</sub>(μ<sub>3</sub>-O)<sub>4</sub>(μ<sub>3</sub>-OH)<sub>4</sub>]<sup>12+</sup> nodes, each linked to 12 carboxylates of terephthalate ligands to form tetrahedral and octahedral cages; however, there are many defects from missing linkers in this MOF, with the resulting otherwise open metal sites occupied by hydroxo ligands.<sup>18-20</sup> The node topology of NU-1000 has been determined to be [Zr<sub>6</sub>(μ<sub>3</sub>-O)<sub>4</sub>(μ<sub>3</sub>-OH)<sub>4</sub>(OH)<sub>4</sub>(OH<sub>2</sub>)<sub>4</sub>]<sup>18+</sup>,<sup>21</sup> and it is coordinated to 8 tetratopic linkers of 1,3,6,8-tetrakis(*p*-benzoic-acid)pyrene (H<sub>4</sub>TBAPy) to form triangular and hexagonal pores. We used Ir(CO)<sub>2</sub>(acac) (acac = acetylacetonate) and Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub>(acac) as precursors to react with functional groups such as OH on the nodes of NU-1000 and UiO-66, accompanied by removal of the acac ligands.<sup>17</sup> The samples were characterized by infrared (IR) and extended X-ray absorption fine structure (EXAFS) spectroscopies as well as density functional theory (DFT) calculations. Our results demonstrate the presence of bonding between the Ir species and node sites and determine their catalytic properties for conversion of ethylene in the presence of H<sub>2</sub>.

## 2. EXPERIMENTAL SECTION

**Synthesis of UiO-66.** ZrCl<sub>4</sub> (0.080 g, 0.343 mmol) and 0.7 mL of acetic acid (modulator) were dissolved in 20 mL of DMF in a 100 mL Teflon-capped glass jar by using ultrasound for 5 min. The linker precursor benzene-1,4-dicarboxylic acid (0.057 g, 0.343 mmol) was then added into the solution and dissolved by ultrasound applied for about 5 min. The jars were kept in an oven at 393 K under static conditions for 24 h. White precipitates were produced, and they were isolated by centrifugation after cooling to room temperature. The solids were washed with DMF three times to remove unreacted precursors and with methanol six times to remove DMF. Then the powder was dried at room temperature.

**Synthesis of NU-1000.** A sample consisting of 97 mg of ZrOCl<sub>2</sub>·8H<sub>2</sub>O (0.30 mmol) and 2700 mg (22 mmol) of benzoic acid was mixed in 8 mL of DMF (in a 6-dram vial) and ultrasonically dissolved. The clear solution was incubated in an oven at 353 K for 1 h. After cooling to room temperature, 40 mg (0.06 mmol) of H<sub>4</sub>TBAPy was added to this solution, and the mixture was sonicated for 20 min. The

yellow suspension was held in an oven at 353 K for 24 h. After cooling to room temperature, yellow polycrystalline material was isolated by filtration (35 mg of activated material, 54% yield) and washed with DMF and subsequently activated with HCl. Then the solid was washed twice with DMF and six times with acetone. The powder was dried at room temperature.

**Synthesis of Ir(CO)<sub>2</sub> and Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub> supported on MOFs.** Sample syntheses and handling were performed with the exclusion of moisture and air by use of a double-mainfold Schlenk vacuum line and an argon-atmosphere glove box.

The precursor Ir(CO)<sub>2</sub>(acac), with 98% purity, was purchased from Strem Chemicals, Inc. The precursor Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub>(acac) was synthesized as described elsewhere;<sup>22</sup> it has been characterized by X-ray diffraction crystallography and <sup>1</sup>H and <sup>13</sup>C NMR, Raman, and IR spectroscopies.

The supported iridium complex was prepared by bringing the precursor Ir(CO)<sub>2</sub>(acac) or Ir(C<sub>2</sub>H<sub>4</sub>)<sub>2</sub>(acac) (36.2 mg for a 10-wt% iridium loading or 3.6 mg for a 1.0-wt% iridium loading) in contact with 200 mg of activated MOF powder (UiO-66 or NU-1000 was activated under vacuum (10<sup>-7</sup> Torr) at 423 or 393 K, respectively, for 24 h before use) in a Schlenk flask and slurried in 40 mL of dried *n*-pentane (Fisher, 99%) at room temperature. After 4 h, the solvent was removed by evacuation for a day, so that all the iridium remained in the MOF. The resultant solids, containing 10 wt% or 1.0 wt% iridium, were stored in the argon-filled glovebox. The iridium loadings were inferred from the conditions of the syntheses, whereby all of the added iridium remained in the MOF.

**Infrared spectroscopy.** A Bruker IFS 66v/S spectrometer with a spectral resolution of 2 cm<sup>-1</sup> was used to collect transmission IR spectra of power samples. Approximately 30 mg of solid sample inside a glove box was pressed into a thin wafer and loaded into a cell that served as a flow reactor (In-situ Research Institute, Inc., South Bend, IN). The cell was sealed and connected to a flow system that allowed recording of spectra while the reactant gases flowed through the cell at reaction temperature. Each spectrum is the average of 64 scans.

**X-ray absorption spectroscopy.** X-ray absorption spectra were recorded at X-ray beamline 4-1 at the Stanford Synchrotron Radiation Lightsource (SSRL). The storage ring electron energy and ring current were 3 GeV and 300 mA, respectively. A double-crystal Si(220) monochromator was detuned by

20–25% at the Ir L<sub>III</sub> edge to minimize the effects of higher harmonics in the X-ray beam.

**Catalytic reaction rates.** Ethylene hydrogenation catalysis was carried out in a conventional laboratory once-through tubular plug-flow reactor at 298 K and 1 bar. The catalyst (10 to 50 mg) was mixed with 10 g of inert, nonporous  $\alpha$ -Al<sub>2</sub>O<sub>3</sub> and loaded into the reactor in the argon-filled glove box. The feed partial pressure was 100 mbar of C<sub>2</sub>H<sub>4</sub>, 200 mbar of H<sub>2</sub>, and 700 mbar of helium, with a total flow rate of 100 mL(NTP)/min. Products were analyzed with an on-line Agilent 6890 gas chromatograph. The ethylene conversions were <5%, and the reactor was well approximated as differential, determining reaction rates directly.


**Computational methods.** Density functional theory, DFT, calculations were performed on neutral cluster models with the M06-L<sup>23</sup> density functional as implemented in the Gaussian 09 software package. In this software package, we used ultrafine grids (99 radial nodes and 590 angular nodes for C, H, and O atoms but 199 radial nodes and 974 angular nodes for Zr and Ir atoms) for numerical integrations. The def2-svp basis set was used for the C, H, and O atoms whereas the def2-tzvp<sup>24-26</sup> basis set and associated effective core potential was employed for Zr and Ir atoms. The positions of all atoms, with the exceptions of the atoms in the aryl organic linkers, were optimized. Vibrational frequency analyses were carried out to confirm the nature of the stationary points found after each geometry optimization. The geometry optimizations and vibrational frequency analyses were carried out for the

samples in the gas-phase as well as in *n*-pentane. The polarizable continuum model (PCM<sup>27</sup>) was used to account for solvation effects for the calculations carried out with the samples in *n*-pentane.

The cluster models were constructed from periodic unit cells of NU-1000 and UiO-66 optimized with the generalized-gradient approximation PBE<sup>28</sup> density functional while using plane wave basis sets within the projector-augmented wave approach as implemented in the Vienna Ab Initio Simulation Package (VASP<sup>29-32</sup>). In these periodic calculations, we used a plane-wave kinetic energy cutoff of 520 eV, a convergence criterion of 0.05 eV/Å for atomic positions, and an automatically generated gamma-centered Monkhorst-Pack k-point grid.

The procedure for generating the cluster models from the optimized periodic structure of NU-1000 has been described.<sup>21</sup> Briefly, the first coordination sphere of the Zr<sub>6</sub>-metalate node is extracted from the periodic structure while truncating the TPAPy<sup>4-</sup> linkers to benzoate groups. A two-step protocol was then used for optimizing the resulting clusters. First, we optimized the positions of the aromatic H atoms while fixing all other atoms. Second, the C<sub>6</sub>H<sub>5</sub> units of the benzoate groups were held fixed while the positions of all other atoms were optimized. A similar procedure was used for UiO-66. However, the linkers in its periodic model were truncated to acetate groups to speed up the computations.

### 3. RESULTS AND DISCUSSION

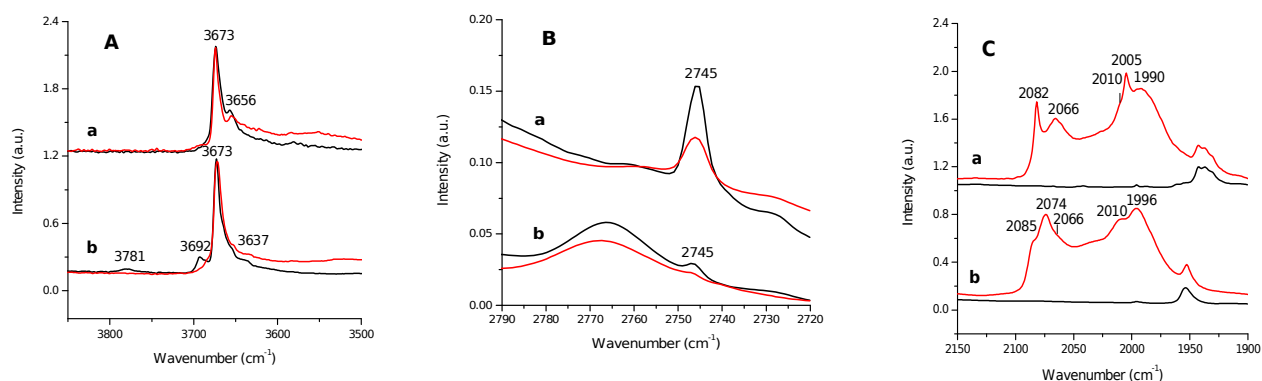

**Figure 1.** IR spectra in (A)  $\nu_{\text{OH}}$  region, (B) H-bonded H<sub>2</sub>O and -OH region and (C)  $\nu_{\text{CO}}$  region characterizing (a) bare NU-1000 and (b) bare UiO-66 (black) and the samples formed by adsorption of Ir(CO)<sub>2</sub>(acac) on them (red).

**Ir(CO)<sub>2</sub> complexes supported on nodes of NU-1000 and of UiO-66.** Ir(CO)<sub>2</sub>(acac) in *n*-pentane solution reacted with NU-1000 nodes, removing the protons in hydrogen-bonded

H<sub>2</sub>O/OH groups,<sup>21</sup> as shown by the decreased intensities of the 2745-cm<sup>-1</sup> band in the IR spectra (Figure 1B), and forming chemisorbed species, assigned, on the basis of new IR bands

at 2066 and 1990  $\text{cm}^{-1}$ , as iridium *gem*-dicarbonyls bonded to two ligands inferred to be oxygen atoms also coordinated to the  $\text{Zr}_6$  node (Figure 2). The iridium loading was 10.0 wt%, corresponding to nearly one Ir atom per node. The  $\nu_{\text{CO}}$  bands shifted to 2017 and 1943  $\text{cm}^{-1}$  when the sample was brought in contact with  $^{13}\text{CO}$  at room temperature, confirming the identification (Figure S2, Table S1, Supporting Information (SI)). EXAFS parameters measured at the Ir  $L_{\text{III}}$  edge confirm the structure, with the coordination numbers and interatomic distances shown in Table 1. This structure closely matches that of  $\text{Ir}(\text{CO})_2$  on a zeolite.<sup>33-36</sup>

$\text{Ir}(\text{CO})_2(\text{acac})$  in *n*-pentane solution reacted similarly with UiO-66 nodes, but, in contrast to NU-1000, UiO-66 reacted with  $\text{Ir}(\text{CO})_2(\text{acac})$  to give two chemisorbed species, identified on the basis of IR spectroscopy, with a pair of  $\nu_{\text{CO}}$  bands at 2074 and 1996  $\text{cm}^{-1}$ , and a band at 2066  $\text{cm}^{-1}$ . Both bands characterizing non-hydrogen-bonded node OH groups, at 3781 and 3692  $\text{cm}^{-1}$  (Figure 1A, Table S2) and hydrogen-bonded node  $\text{H}_2\text{O}/\text{OH}$  species, at 2745  $\text{cm}^{-1}$  (Figure 1B), decreased in intensity as a result of the chemisorption reaction, indicating the participation of these groups, in this case associated with site defects (see below). Correspondingly, the pore volumes of the MOFs decreased (Section S4, SI).

**Table 1.** EXAFS and calculated DFT structural parameters of  $\text{Ir}(\text{CO})_2$  supported on NU-1000  $\text{Zr}_6$  nodes.<sup>a</sup>

| Shell              | EXAFS                                       |                   |     |                      | DFT                  |
|--------------------|---|-------------------|-----|----------------------|----------------------|
|                    | $10^3 \times \Delta\sigma^2 (\text{\AA}^2)$ | $\Delta E_0$ (eV) | $N$ | $R$ ( $\text{\AA}$ ) | $R$ ( $\text{\AA}$ ) |
| Ir-O <sub>t</sub>  | 5.4   | -5.2              | 2.0 | 2.05                 | 2.11                 |
| Ir-C <sub>co</sub> | 14.6  | -5.9              | 2.1 | 1.97                 | 1.83                 |
| Ir-O <sub>co</sub> | 14.5  | 7.4               | 2.1 | 2.99                 | 2.98                 |
| Ir-O <sub>b</sub>  | 6.8   | -5.6              | 1.9 | 3.13                 | 3.39                 |
| Ir-Zr              | 14.2  | -0.7              | 2.0 | 3.55                 | 3.72                 |


<sup>a</sup>Notation: O<sub>t</sub>, O atoms of terminal -OH groups on  $\text{Zr}_6$  node; C<sub>co</sub>, carbonyl carbon; O<sub>co</sub>, carbonyl oxygen; O<sub>b</sub>, O in bridging  $\mu_3$ -OH or  $\mu_3$ -O group on  $\text{Zr}_6$  node;  $N$ , coordination number;  $R$ , distance between absorber and back-scatterer atoms;  $\Delta\sigma^2$ , disorder term;  $\Delta E_0$ , inner

potential correction. Estimated EXAFS error bounds:  $N$ ,  $\pm 20\%$ ;  $R$ ,  $\pm 0.02 \text{ \AA}$ ;  $\Delta\sigma^2$ ,  $\pm 20\%$ ;  $\Delta E_0$ ,  $\pm 20\%$  (errors characterizing the Ir-Zr contribution are greater); fit range:  $3.87 < k$  (wave vector)  $< 13.61 \text{ \AA}^{-1}$ ;  $0.5 < R < 4 \text{ \AA}$ ; goodness of fit value 3.5.


At the high loading of 10 wt% iridium, we also detected physisorbed  $\text{Ir}(\text{CO})_2(\text{acac})$  on each MOF, as shown by the IR bands at 2085 and 2010  $\text{cm}^{-1}$  (Figure 1C), which are close in frequency to those characterizing  $\text{Ir}(\text{CO})_2(\text{acac})$  in *n*-hexane solution<sup>37</sup>. Because the pore aperture of UiO-66 ( $\sim 6 \text{ \AA}$ )<sup>18</sup> is barely greater than the narrowest dimension of the precursor ( $\sim 4 \times 6 \text{ \AA}$ ), we infer that the supported iridium species were present preferentially near the external UiO-66 particle surfaces.<sup>38,39</sup> The 2010- $\text{cm}^{-1}$  band is also evident in the spectrum of the NU-1000-supported species, and it disappeared after 8 h of contact of the precursor with this MOF, during which time two sharp bands, at 2082 and 2005  $\text{cm}^{-1}$  (also assigned to physisorbed  $\text{Ir}(\text{CO})_2(\text{acac})$ , Figure 1C) decreased in intensity and then disappeared after 20 h (Figure S5). Because these disappeared slowly, we suggest that they were indicative of iridium-containing species on the internal NU-1000 surface and that their removal was slowed by their diffusion in the narrow pores.

To determine the structures of the iridium-supporting sites, we performed DFT calculations characterizing the structure of iridium complexes on neutral cluster models of NU-1000. The calculations for NU-1000 show that the most stable iridium complexes are situated in the MOF channels, with the metal atom replacing the proton in a terminal  $\text{OH}_2$  group that otherwise bridges to an adjacent terminal OH group on the node (Figure 2). The result is consistent with the experimental observation showing a decreased intensity of the H-bonded  $\text{H}_2\text{O}$  and -OH band at 2745  $\text{cm}^{-1}$  after reaction of  $\text{Ir}(\text{CO})_2(\text{acac})$  with NU-1000 (Figure 1B). To confirm, the assignment of the IR band at 2745  $\text{cm}^{-1}$ , we note that DFT predicts that this vibration will be found at approximately 2851 and 2875  $\text{cm}^{-1}$ . Application of a scaling factor of 0.956 changes these calculated values to 2726 and 2749  $\text{cm}^{-1}$ , in good agreement with the experiment. The choice of this scaling factor is discussed below.



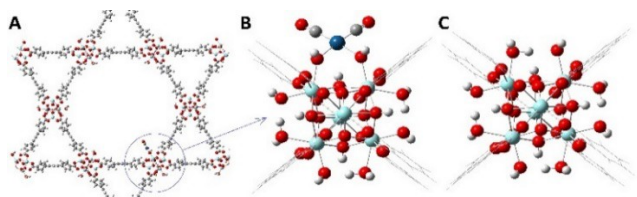

**Figure 2.**  $\text{Ir}(\text{CO})_2$  deposited onto the  $\text{Zr}_6$  nodes of NU-1000. (A) The location of the iridium complex in a periodic crystal of NU-1000. (B) Expanded view of the iridium complex at the  $\text{Zr}_6$  node. (C) The same site in pristine NU-1000 prior to  $\text{Ir}(\text{CO})_2$  complexation.

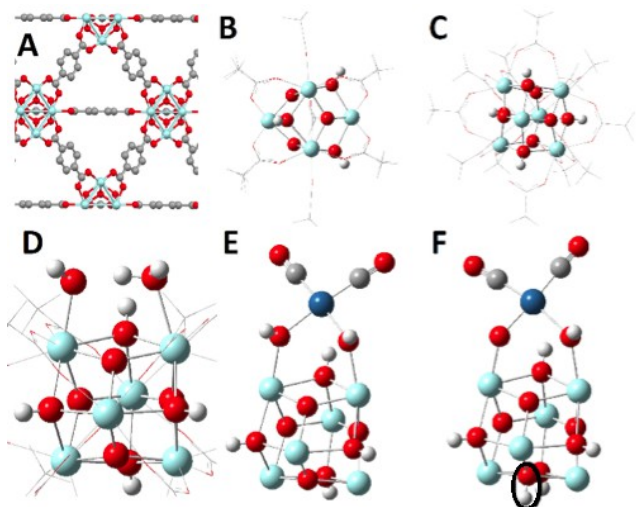

**Figure 3.** A, Periodic structure showing the pore channels of UiO-66. B, Model cluster representing the  $\text{Zr}_6$  node. C, Same model cluster rotated 90 degrees about the horizontal axis. D, A ligand defect with terminal  $-\text{OH}$  and  $\text{OH}_2$  groups replacing a missing linker. E, *Site 1* complexation of  $\text{Ir}(\text{CO})_2$ . F, *Site 2* complexation of  $\text{Ir}(\text{CO})_2$  (with “extra”  $\mu_3\text{-OH}$  group circled in black).

The calculated structural parameters for this binding mode, Figure 2, are compared with EXAFS data in Table 1. Agreement is generally good, although the distances between the Ir atoms and bridging O or Zr atoms of the node are overestimated by 0.2-0.3 Å, consistent with results of analogous combined DFT/EXAFS<sup>40,41</sup> investigations. The calculated  $\nu_{\text{CO}}$  bands of this binding mode are 2157 and 2085  $\text{cm}^{-1}$ . Alecu *et al.*<sup>42</sup> determined scale factors of 0.951-0.958 for fundamental vibrational frequencies obtained with various M06-L model chemistries; a scaling factor of 0.956 brings the calculated frequencies of the two  $\nu_{\text{CO}}$  bands to 2062 and 1993  $\text{cm}^{-1}$ , both within 4  $\text{cm}^{-1}$  of experiment, Figure 1C. The calculated separation of the bands (69  $\text{cm}^{-1}$  after scaling) matches experiment (76  $\text{cm}^{-1}$ ) to within 10%.


On UiO-66 (Figure 3A-C) there are three possible types of defects that can be created by the loss of an organic linker (Section 8, SI). The most stable defect is shown in Figure 3D and offers a binding site (*site 1*) similar to that of NU-1000 (Figure 2C). The decrease of the hydrogen-bonded  $\text{H}_2\text{O}$  and  $-\text{OH}$  band at 2745- $\text{cm}^{-1}$  (Figure 1B) indicates the reaction of  $\text{Ir}(\text{CO})_2(\text{acac})$  with *site 1* on UiO-66. After bonding of  $\text{Ir}(\text{CO})_2$  to this defect, Figure 3E, we calculate unscaled  $\nu_{\text{CO}}$  bands of 2165 and 2090  $\text{cm}^{-1}$ , very similar to those obtained for NU-1000 and corresponding to the lower-frequency pair observed experimentally, Figure 1C. The structural parameters of this complex are very similar to those in Table 1 for NU-1000. At the M06-L level, formation of  $\text{Ir}(\text{CO})_2$  supported at *site 1* from  $\text{Ir}(\text{CO})_2(\text{acac})$  is calculated to be exoergic by -4.3 kcal/mol.

After consideration of a number of possibilities, and an assessment of their energies, we assign the second site (*site 2*) for adsorption of  $\text{Ir}(\text{CO})_2$  on UiO-66 as shown in Figure 3F. In this case a proton has migrated from one coordinating OH group to a  $\mu_3\text{-O}$  oxo group (creating an additional  $\mu_3\text{-OH}$  group, Figure 3F). The above mentioned non-hydrogen-bonded OH bands at 3781 and 3692  $\text{cm}^{-1}$  are calculated to be the hydroxyl groups of *site 2* (Table S2). They disappeared after reaction of  $\text{Ir}(\text{CO})_2(\text{acac})$  with these sites. These bands were calculated as being at approximately 3947 and 3875  $\text{cm}^{-1}$ , respectively, from our DFT calculations. Again, application of the scaling factor brings good agreement with empirical data (3773 and 3704  $\text{cm}^{-1}$ , respectively).

The unscaled calculated  $\nu_{\text{CO}}$  bands for the resulting  $\text{Ir}(\text{CO})_2$  complex at *site 2* are 2173 and 2104  $\text{cm}^{-1}$ , corresponding to the higher-frequency pair observed experimentally, Figure 1C. When the scaling factor of 0.956 is applied to the four computed values (giving 2070 and 1998  $\text{cm}^{-1}$  for *site 1* and 2077 and 2011  $\text{cm}^{-1}$  for *site 2*), the mean unsigned error comparing to experimental values is 8  $\text{cm}^{-1}$ , offering good support for these structural assignments. We note that the higher carbonyl stretching frequencies associated with *site 2* suggest less back donation from Ir into acceptor  $\pi^*_{\text{CO}}$  orbitals. Consistent with this analysis, calculated partial atomic charges on the Ir center are more positive in *site 2* (Hirshfeld:<sup>43</sup> 0.29; Mulliken:<sup>44</sup> 0.51) than in *site 1* (Hirshfeld: 0.17; Mulliken: 0.36).

We emphasize that  $\text{Ir}(\text{CO})_2(\text{acac})$  did not react with the bridging  $\mu_3\text{-OH}$  groups on the  $\text{Zr}_6$  nodes, characterized by the IR band at 3673  $\text{cm}^{-1}$ , as indicated by the lack of change of this band, either on NU-1000 or UiO-66, after

anchoring of the iridium precursor (Figure 1A). DFT calculations confirm that reaction of  $\text{Ir}(\text{CO})_2$  groups with the bridging  $\mu_3\text{-OH}$  groups found at defects in UiO-66 is endoergic by about 28 kcal/mol—a value that is in marked contrast to the calculated reaction energies for the deposition of  $\text{Ir}(\text{CO})_2$  on *site 1* (-4.3 kcal/mol) and *site 2* (1.2 kcal/mol).

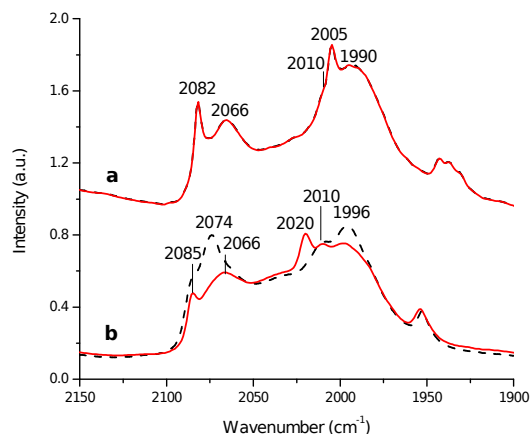


**Figure 4.** IR spectra in the  $\nu_{\text{CO}}$  region characterizing in the sample initially formed by the chemisorption of  $\text{Ir}(\text{CO})_2(\text{acac})$  on (a) NU-1000 and (b) UiO-66 as initially present (dashed, black) and after exposure to flowing ethylene at 298 K and 1 bar for 20 min (red).

$\text{Ir}(\text{CO})_2$  supported on the MOFs, when treated with flowing  $\text{C}_2\text{H}_4$ , underwent a limited ligand exchange reaction, sometimes leading to replacement of one CO by  $\text{C}_2\text{H}_4$ , but only for *site 2* in the UiO-66 complex. In that case, a new band at  $2020\text{ cm}^{-1}$  was observed and assigned to  $\text{Ir}(\text{CO})(\text{C}_2\text{H}_4)$  (Figure 4).

**$\text{Ir}(\text{C}_2\text{H}_4)_2$  complexes supported on the nodes of NU-1000 and UiO-66.** Supported  $\text{Ir}(\text{C}_2\text{H}_4)_2$  complexes were prepared alternatively from reactions with pristine MOFs employing precursor  $\text{Ir}(\text{C}_2\text{H}_4)_2(\text{acac})$  in a fashion analogous to that for  $\text{Ir}(\text{CO})_2(\text{acac})$ . IR data (Figure S6 and S7, SI) indicate that  $\text{Ir}(\text{C}_2\text{H}_4)_2$  also adsorbs onto the nodes, again with single iridium complexes on NU-1000 and a mixture on UiO-66. We sought to prepare supported catalysts dominated by the species analogous to those characterized above, rather than more complex mixtures, by using low loadings of iridium on the supports (1 wt %). At this loading, IR spectra (Figure 5) are consistent with the supports being nearly ideal, and these well-defined samples were tested as catalysts for ethylene conversion in a once-through flow

reactor in the presence of  $\text{H}_2$  at 300 K and 1 bar.

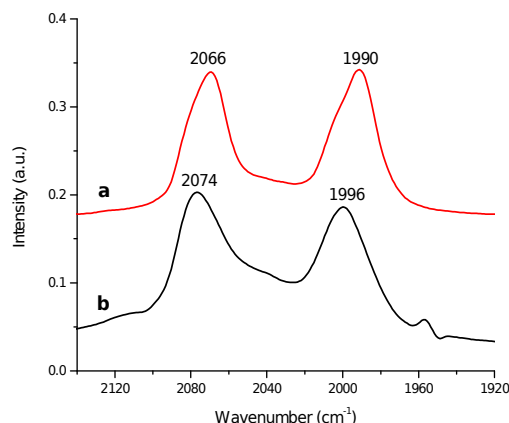

**Figure 5.** IR spectra in the  $\nu_{\text{CO}}$  region characterizing the sample initially the sample formed by the adsorption of  $\text{Ir}(\text{C}_2\text{H}_4)_2(\text{acac})$  (with iridium loading 1%) on (a) NU-1000 and (b) UiO-66 after exposure to flowing CO 10%/He at 298 K and 1 bar for 2 min.


**Table 2.** Catalytic activities of MOF node-supported iridium complexes for hydrogenation and dimerization of ethylene in a flow reactor at 298 K and 1 bar<sup>a</sup>

| Sup<br>port     | TOF,<br>s <sup>-1</sup> | Selectivity under differential<br>conversion conditions, mol% |            |            |                                |              |                              |
|-----------------|-------------------------|---|------------|------------|--------------------------------|--------------|------------------------------|
|                 |                         | etha<br>ne  | buta<br>ne | bute<br>ne | butene isomers                 |              |                              |
|                 |                         |   |            |            | <i>trans</i> -<br>2-bute<br>ne | 1-but<br>ene | <i>cis</i> -<br>2-bute<br>ne |
| NU-<br>100<br>0 | 0.01<br>0               | 99.5  | 0          | 0.5        | 0                              | 0.5          | 0                            |
| UiO-<br>66      | 0.01<br>7               | 98.5  | 0.1        | 1.1        | 0.2                            | 0.8          | 0.1                          |

<sup>a</sup>There was no detectable catalytic reaction in the absence of the catalyst under our conditions, and the MOF alone was catalytically inactive. <sup>b</sup>Support for catalyst initially incorporating node-anchored  $\text{Ir}(\text{C}_2\text{H}_4)_2$ ; <sup>b</sup>turnover frequency determined from  $\text{C}_2\text{H}_4$  conversions < 5%; catalyst mass: 10–50 mg; feed partial pressures: 100 mbar  $\text{C}_2\text{H}_4$ , 200 mbar  $\text{H}_2$ , 700 mbar helium; total flow rate 100 mL(NTP)/min.

The supported  $\text{Ir}(\text{C}_2\text{H}_4)_2$  complexes were found to be precatalysts for ethylene hydrogenation

accompanied by slight ethylene dimerization (Table 2), with the activity and selectivity both depending on which MOF was used as the support. As noted above, the iridium center of *site 2* is more electropositive (or electrophilic) than that of *site 1* in the  $\text{Ir}(\text{CO})_2$  complexes. This pattern extends to the corresponding  $\text{Ir}(\text{C}_2\text{H}_4)_2$ ,  $\text{Ir}(\text{CO})(\text{C}_2\text{H}_4)$ ,  $\text{Ir}(\text{CO})(\text{C}_2\text{H}_4)(\text{H}_2)$ , and  $\text{Ir}(\text{C}_2\text{H}_4)_2(\text{H}_2)$  species as well. Thus, the nature of the MOF support affects the transition states and activation energies for the various catalytic reactions. In Figure 6, for instance, the calculated barriers for ethylene dimerization catalysis via an intermediate metallacycle are lower for *site 2* of UiO-66 than for *site 1*. Insofar as the NU-1000 catalytic site is analogous to the UiO-66 *site 1*, Figure 6, this result rationalizes the increased dimerization selectivity observed for UiO-66 and is also consistent with IR data suggesting that *site 2* dominates the catalytic reactivity of UiO-66.

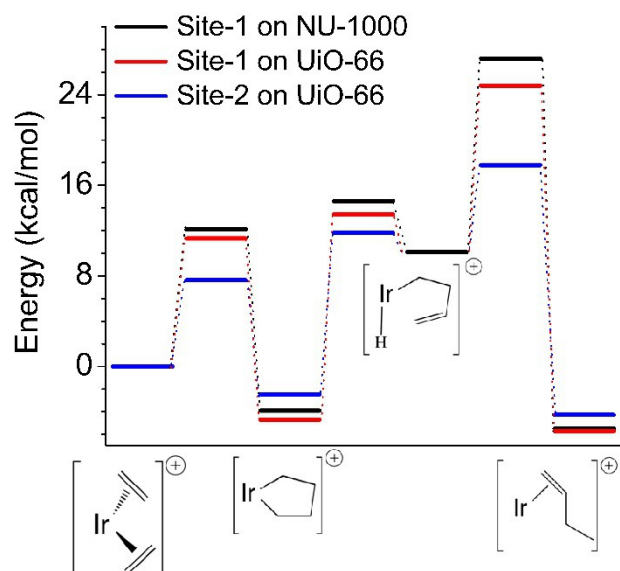

**Figure 6.** Calculated pathway for the dimerization of ethylene to 1-butene at *site 1* and *site 2* for  $\text{Ir}(\text{C}_2\text{H}_4)_2$  on UiO-66 and NU-1000 at M06-L level (the MOF nodes as counteranions are implicit). More details are available in Section S8, SI.

Competing reaction mechanisms for ethylene dimerization were explored; the one reported in Figure 6 was found to be energetically the most favorable. The pathway for ethylene hydrogenation was also investigated, and the results show that hydrogenation is favored over dimerization because of the lower calculated barriers (2-12 kcal/mol for hydrogenation, Section S8, SI, versus 8-19 kcal/mol for dimerization, Figure 6) and the weak adsorption of ethane on the iridium sites (relative to alkenes), which favors desorption of this product, Table 2.

We probed the used catalysts (after 1 h of continuous ethylene hydrogenation) with a pulse of CO introduced into the feed stream. The results (Figure S8, SI) indicate the formation of the iridium *gem*-dicarbonyl bands essentially matching those of the fresh catalyst and thereby demonstrating the stability of the mononuclear iridium complexes under catalytic reaction conditions.

#### 4. CONCLUSIONS

In summary, the nodes of NU-1000 and UiO-66 MOFs are essentially molecular catalyst supports upon which highly uniform catalytic metal complexes can be chemisorbed. These are among the simplest and best defined of any supported metal species, constituting, we infer, an emerging class of materials that may offer broad opportunities for discovery of new catalysts guided by theory. We may expect high selectivities associated with the uniformity of the catalytic species and high stabilities when combinations of metals and MOFs are appropriately chosen.

#### ASSOCIATED CONTENT

**Supporting Information.** Experimental and computational details are reported. This material is available free of charge via the Internet at <http://pubs.acs.org>.

#### AUTHOR INFORMATION

##### Corresponding Author

- \* [bccgates@ucdavis.edu](mailto:bccgates@ucdavis.edu) (B.C.G.)
- \* [gagliard@umn.edu](mailto:gagliard@umn.edu) (L.G.)

##### Notes

The authors declare no competing financial interests.

#### ACKNOWLEDGMENT

This work was supported as part of the Inorganometallic Catalyst Design Center, an Energy Frontier Research Center funded by the U.S. Department of Energy (DOE), Office of Science, Basic Energy Sciences (BES), under Award DE-SC0012702.


#### REFERENCES

- (1) Furukawa, H.; Cordova, K. E.; O'Keeffe, M.; Yaghi, O. M. *Science* **2013**, 341, 974.
- (2) Ferey, G. *Chem. Soc. Rev.* **2008**, 37, 191.
- (3) Horike, S.; Shimomura, S.; Kitagawa, S. *Nat. Chem.* **2009**, 1, 695.
- (4) Corma, A.; Garcia, H.; Llabres i Xamena, F. X. *Chem. Rev.* **2010**, 110, 4606.
- (5) Lee, J.; Farha, O. K.; Roberts, J.; Scheidt, K. A.; Nguyen, S. T.; Hupp, J. T. *Chem. Soc. Rev.* **2009**, 38, 1450.
- (6) Gascon, J.; Corma, A.; Kapteijn, F.; Llabres i Xamena, F. X. *ACS Catal.* **2014**, 4, 361.
- (7) Farrusseng, D.; Aguado, S.; Pinel, C. *Angew. Chem. Int. Ed.* **2009**, 48, 7502.



- (8) Dhakshinamoorthy, A.; Alvaro, M.; Garcia, H. *Catal. Sci. Technol.* **2011**, 1, 856.
- (9) Ma, L. Q.; Abney, C.; Lin, W. B. *Chem. Soc. Rev.* **2009**, 38, 1248.
- (10) Yoon, M.; Srirambalaji, R.; Kim, K. *Chem. Rev.* **2012**, 112, 1196.
- (11) Manna, K.; Zhang, T.; Carboni, M.; Abney, C. W.; Lin, W. B. *J. Am. Chem. Soc.* **2014**, 136, 13182.
- (12) Fei, H. H.; Cohen, S. M. *J. Am. Chem. Soc.* **2015**, 137, 2191.
- (13) Gonzalez, M. I.; Bloch, E. D.; Mason, J. A.; Teat, S. J.; Long, J. R. *Inorg. Chem.* **2015**, 54, 2995.
- (14) Larabi, C.; Quadrelli, E. A. *Eur. J. Inorg. Chem.* **2012**, 3014.
- (15) Nguyen, H. G. T.; Schweitzer, N. M.; Chang, C. Y.; Drake, T. L.; So, M. C.; Stair, P. C.; Farha, O. K.; Hupp, J. T.; Nguyen, S. T. *ACS Catal.* **2014**, 4, 2496.
- (16) Mondloch, J. E.; Bury, W.; Fairen-Jimenez, D.; Kwon, S.; DeMarco, E. J.; Weston, M. H.; Sarjeant, A. A.; Nguyen, S. T.; Stair, P. C.; Snurr, R. Q.; Farha, O. K.; Hupp, J. T. *J. Am. Chem. Soc.* **2013**, 135, 10294.
- (17) Serna, P.; Gates, B. C. *Acc. Chem. Res.* **2014**, 47, 2612.
- (18) Cavka, J. H.; Jakobsen, S.; Olsbye, U.; Guillou, N.; Lamberti, C.; Bordiga, S.; Lillerud, K. P. *J. Am. Chem. Soc.* **2008**, 130, 13850.
- (19) Cliffe, M. J.; Wan, W.; Zou, X. D.; Chater, P. A.; Kleppe, A. K.; Tucker, M. G.; Wilhelm, H.; Funnell, N. P.; Coudert, F. X.; Goodwin, A. L. *Nat. Commun.* **2014**, 5.
- (20) Vermoortele, F.; Bueken, B.; Le Bars, G.; Van de Voorde, B.; Vandichel, M.; Houthoofd, K.; Vimont, A.; Daturi, M.; Waroquier, M.; Van Speybroeck, V.; Kirschhock, C.; De Vos, D. E. *J. Am. Chem. Soc.* **2013**, 135, 11465.
- (21) Planas, N.; Mondloch, J. E.; Tussupbayev, S.; Borycz, J.; Gagliardi, L.; Hupp, J. T.; Farha, O. K.; Cramer, C. J. *J. Phys. Chem. Lett.* **2014**, 5, 3716.
- (22) Bhirud, V. A.; Uzun, A.; Kletnieks, P. W.; Craciun, R.; Haw, J. F.; Dixon, D. A.; Olmstead, M. M.; Gates, B. C. *J. Organomet. Chem.* **2007**, 692, 2107.
- (23) Zhao, Y.; Truhlar, D. G. *J. Chem. Phys.* **2006**, 125.
- (24) Metz, B.; Stoll, H.; Dolg, M. *J. Chem. Phys.* **2000**, 113, 2563.
- (25) Weigend, F. *Phys. Chem. Chem. Phys.* **2006**, 8, 1057.
- (26) Weigend, F.; Ahlrichs, R. *Phys. Chem. Chem. Phys.* **2005**, 7, 3297.
- (27) Cossi, M.; Rega, N.; Scalmani, G.; Barone, V. *J. Comput. Chem.* **2003**, 24, 669.
- (28) Perdew, J. P.; Burke, K.; Ernzerhof, M. *Phys. Rev. Lett.* **1996**, 77, 3865.
- (29) Kresse, G.; Furthmuller, J. *Phys. Rev. B* **1996**, 54, 11169.
- (30) Kresse, G.; Hafner, J. *Phys. Rev. B* **1994**, 49, 14251.
- (31) Kresse, G.; Hafner, J. *Phys. Rev. B* **1993**, 47, 558.
- (32) Kresse, G.; Furthmuller, J. *Comp. Mater. Sci.* **1996**, 6, 15.
- (33) Lu, J.; Serna, P.; Aydin, C.; Browning, N. D.; Gates, B. C. *J. Am. Chem. Soc.* **2011**, 133, 16186.
- (34) Miessner, H. *J. Am. Chem. Soc.* **1994**, 116, 11522.
- (35) Uzun, A.; Bhirud, V. A.; Kletnieks, P. W.; Haw, J. F.; Gates, B. C. *J. Phys. Chem. C* **2007**, 111, 15064.
- (36) Wu, H.; Chua, Y. S.; Krungleviciute, V.; Tyagi, M.; Chen, P.; Yildirim, T.; Zhou, W. *J. Am. Chem. Soc.* **2013**, 135, 10525.
- (37) Bonati, F.; Ugo, R. *J. Organomet. Chem.* **1968**, 11, 341.
- (38) Lu, J.; Aydin, C.; Browning, N. D.; Gates, B. C. *Langmuir* **2012**, 28, 12806.
- (39) Ogino, I.; Chen, C. Y.; Gates, B. C. *Dalton Trans.* **2010**, 39, 8423.
- (40) Delgado, M.; Santini, C. C.; Delbecq, F.; Baudouin, A.; De Mallmann, A.; Prestipino, C.; Norsic, S.; Sautet, P.; Basset, J.-M. *J. Phys. Chem. C* **2011**, 115, 6757.
- (41) Williams, L. A.; Guo, N.; Motta, A.; Delferro, M.; Fragala, I. L.; Miller, J. T.; Marks, T. J. *Proc. Nat. Acad. Sci. U.S.A.* **2013**, 110, 413.
- (42) Alecu, I. M.; Zheng, J. J.; Zhao, Y.; Truhlar, D. G. *J. Chem. Theory Comput.* **2010**, 6, 2872.
- (43) Hirshfeld, F. L. *Theor. Chem. Acc.* **1977**, 44, 129.
- (44) Mulliken, R. S. *J. Chem. Phys.* **1955**, 23, 1833.

## SYNOPSIS TOC

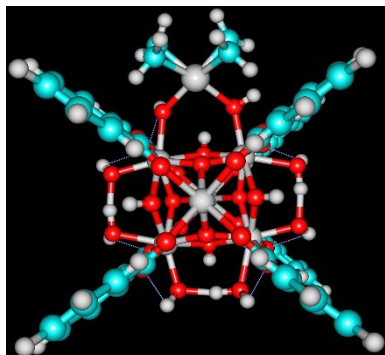

---

X